

Nb₃Sn MATERIALS STUDIES*

S. Posen[†], M. Liepe

Cornell Laboratory for Accelerator-Based Sciences and Education, Ithaca, NY 14853, USA

T. Proslie, ANL, Argonne, IL 60439, USA

Abstract

Nb₃Sn is a very promising material for use in SRF cavity applications, potentially offering significant improvements in quality factor and energy gradient compared to niobium. In order to better understand how to optimize this material for SRF applications, Nb₃Sn samples were prepared at Cornell via vapor deposition, using varying parameters in the coating process. Microscopic studies were performed with SEM/EDX, and studies were performed on bulk samples to measure secondary electron yield, energy gap, and upper critical magnetic field. The results are presented here, with discussion for how they might point the way towards reaching even higher fields in Nb₃Sn cavities.

INTRODUCTION

Nb₃Sn is a material with great potential for SRF applications, offering large potential gains in quality factor and energy gradient compared to niobium due to its large critical temperature T_c and predicted superheating field [1]. At Cornell, infrastructure has been developed to coat single cell 1.3 GHz niobium SRF cavities with Nb₃Sn using the vapor deposition technique, as described in [2]. The first cavities produced have had very promising RF performances, achieving quality factors above 10^{10} at 4.2 K and 13 MV/m [3]. In order to push performance further, it is important to better understand this material. Its superconducting behavior is determined by its properties on the length scale of the coherence length (approximately 3-4 nm) and the penetration depth (approximately 100 nm), so it must be examined on this scale in order to make correlations to its SRF properties. In this paper, we present the results of both bulk and microscopic studies of Nb₃Sn samples designed to better understand and improve the material and the fabrication process.

SEM/EDX AFTER NORMAL COATING

The standard coating process (including annealing step discussed in [3]) produces Nb₃Sn grains with size of approximately 2 μm on top of the much larger niobium grains. Figure 1 shows the Nb₃Sn surface imaged by SEM with a tilt of 52 degrees to show the texture. There are flat facets visible in many grains, as well as smooth curves, and many of the grains have what appear to be indented regions near the middle. EDX scans performed in several regions show a stoichiometry of 24 ± 1 atomic percent tin.

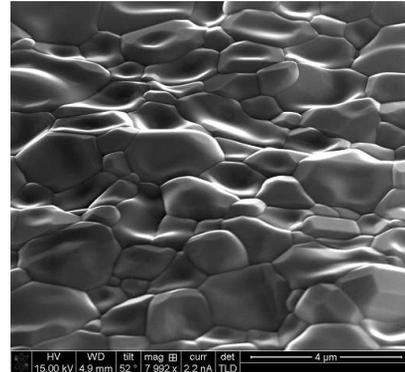


Figure 1: Nb₃Sn surface after coating with the standard recipe. The sample is tilted at 52 degrees with respect to the detector to highlight three dimensional features.

SEM/EDX WITH LG SUBSTRATES

Several small samples were fabricated for experimenting with different Nb₃Sn coating conditions, including some made from large grain niobium. After coating, these samples showed some structures not observed on fine grain niobium. SEM images show the 1-2 μm sized grains usually observed along with localized “clumps.” These regions, which appear as dark areas with size on the order of 10 μm , have a lower tin content, as measured by EDX, by up to 10 atomic percent. Two images taken from samples coated without the usual nucleation agent, SnCl₂, are shown in Fig. 2 (these structures are also observed on LG samples when coating with SnCl₂).

In RF measurements of cavities, a dramatic reduction in Q -slope was observed after an annealing step was added, indicating that the grain structure may strongly influence RF properties. Therefore, studies like this are important to understand how the substrate and coating process influence the grain structure.

SEM/EDX BEFORE/AFTER HF RINSE

For the first time, a niobium cavity with an electropolished surface was coated with Nb₃Sn, and EP samples were coated with it. An SEM image is seen in Fig. 3. The sample was later given 5 cycles of HF rinsing, the same treatment given to a cavity that caused it to have strong Q -slope. SEM of the HF-rinsed surface showed unusual structures on top of the Nb₃Sn grains, which might be the source of the extra losses. EDX was used to probe the structures, but no sign of contamination was measured, and no change in atomic

search Shared Facilities which are supported through the NSF MRSEC program (DMR-1120296).

[†] sep93@cornell.edu

* Work supported by NSF Career award PHY-0841213 and DOE award ER41628. This work made use of the Cornell Center for Materials Re-

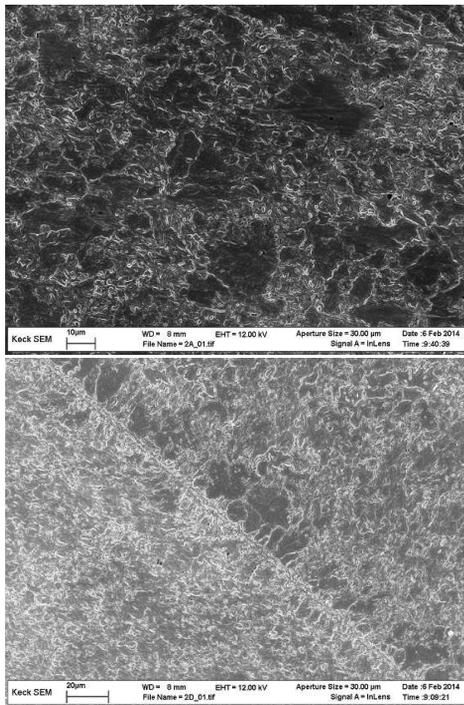


Figure 2: Large grain niobium coated with Nb₃Sn appears to have some regions with large “clumps” along with the usual grains. Shown is a sample coated without nucleation agent, both far from (top) and including (bottom) a grain boundary of the LG substrate. The niobium grain boundary’s influence on the grain structure of the Nb₃Sn is clearly observed.

percent composition of the elements normally observed on the surface (Nb, Sn, O, and a small amount of C) was observed within the resolution of the tool. Auger analysis is planned to achieve higher resolution. It is hoped that these studies will lead to a better understanding of the cavity performance degradation so that a defect removal process can be developed that does not cause *Q*-slope.

TEM SAMPLE PREPARATION

TEM with elemental analysis would allow detailed studies to be done of very small features, such as grain boundary structure and composition, change in tin concentration as a function of depth, and the interface of niobium with Nb₃Sn. To be able to transmit electrons through a sample, it must be very thin, on the order of tens of nm, making TEM samples very difficult to prepare. Two methods were attempted, shown in Fig. 4: mechanical polishing with a diamond lapping film and ion milling via focused ion beam (FIB). The mechanically polished sample was TEM-transparent, but EDX revealed no remaining tin. It is possible that the Nb₃Sn layer was removed during polishing. The first sample prepared with FIB was too thick to allow transmission. Next steps will focus on preparing a thin enough sample with FIB.

03 Technology

3A Superconducting RF

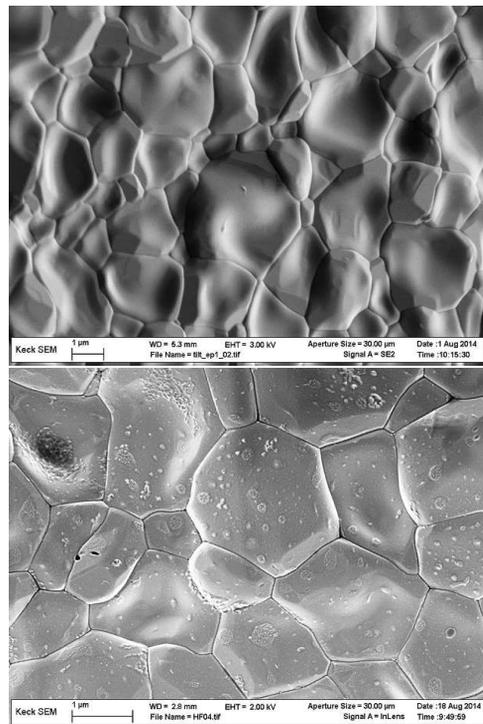


Figure 3: Nb₃Sn coated on an EP Nb surface before (top) and after (bottom) HF rinsing. Note the structures found after rinsing.

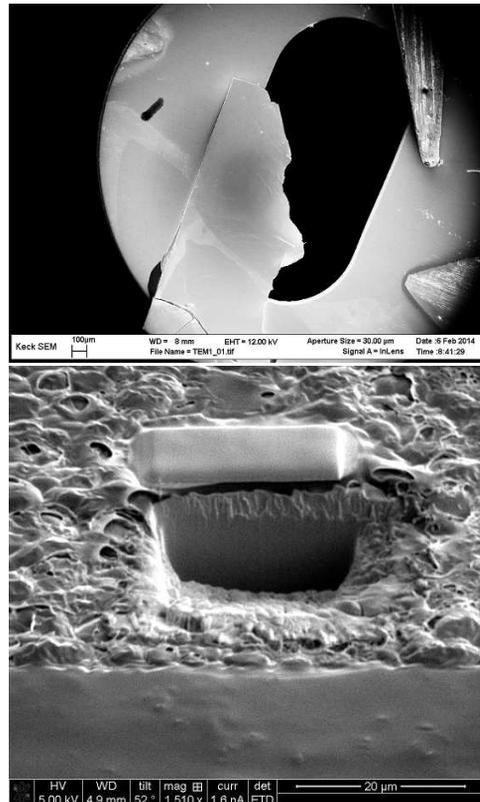


Figure 4: Attempts to make TEM-transparent samples via mechanical polishing with a diamond lapping film (top) and ion milling (bottom). Further effort will be needed to extract usable TEM samples.

BULK MEASUREMENTS

Secondary electron yield (SEY) measurements were performed by S. Aull at CERN on a Nb₃Sn sample provided by Cornell. The maximum SEY was found to be 2.5, very similar to niobium, suggesting that multipacting in Nb₃Sn cavities should be comparable to that normally observed in Nb cavities [4].

Point contact tunneling (PCT) measurements were performed at Argonne on a Nb₃Sn sample provided by Cornell. Correlations with temperatures gave an energy gap Δ at zero temperature of approximately 2.89 meV with a T_c of 16 K. These values (combined with composition from EDX) appear to follow correlations found in the literature [5], as shown in Fig. 5. Note that the PCT curves show a nice, sharp gap at low temperatures.

H_{c2} measurements were also performed at Argonne on the same Cornell Nb₃Sn sample, using a 50% resistive criterion (where the transition is taken to occur when the resistance is half of the normal conducting value). As shown in Fig. 6, the extrapolated value for H_{c2} at zero temperature of 17.9 T appears to follow correlations found in the literature [5]. H_{c2} calculated from material parameters extracted from impedance measurements during RF tests is also shown [3].

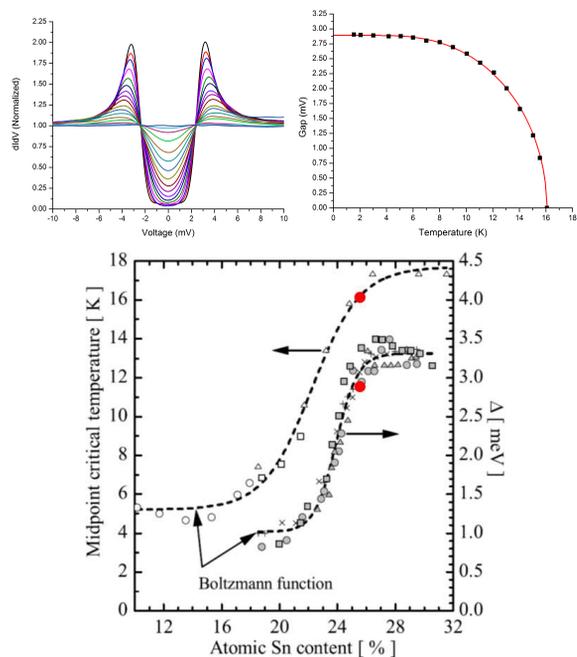


Figure 5: Top left: Point contact tunneling measurements made at several different temperatures. Top right: extraction of T_c and Δ . Bottom: Comparison of extracted values (red) to literature with figure adapted from [5].

CONCLUSIONS

SEM/EDX studies were performed on Nb₃Sn coatings on large grain substrates and electropolished substrates. The large grain substrates showed broad “clumps” of low tin content material. SEM of HF rinsed samples showed un-

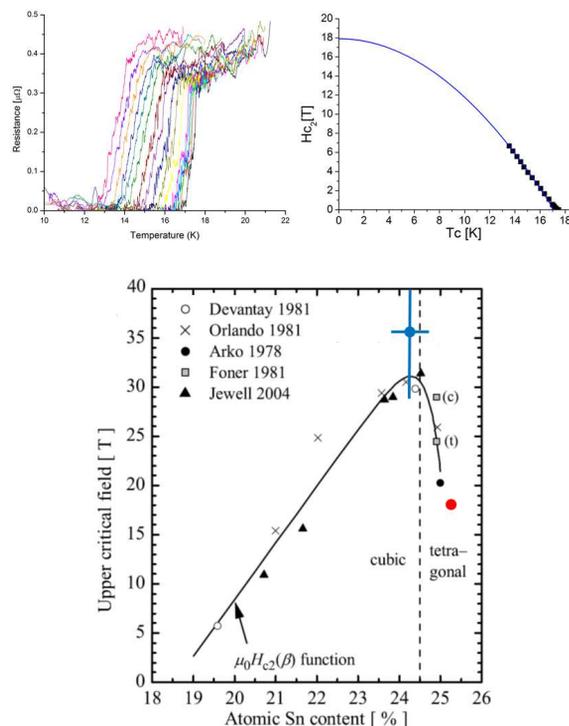


Figure 6: Top left: Resistive measurements made at several different external fields. Top right: extraction of H_{c2} extrapolated to zero temperature with 50% resistive criterion. Bottom: Extracted value from H_{c2} measurements (red) and computed value from material parameters generated extracted from impedance measurements during RF tests (blue) are compared to literature with figure adapted from [5].

usual structures, perhaps explaining performance degradation observed in RF tests after HF rinse. SEY, PCT, and high magnetic field measurements were performed on bulk samples. SEY measurements indicate that vulnerability to multipacting should be similar to that in niobium cavities. Δ and H_{c2} extracted from PCT and magnetic measurements appeared to follow trends from the literature, demonstrating the high quality of the Nb₃Sn coatings fabricated at Cornell.

ACKNOWLEDGEMENTS

The authors would like to express special thanks to S. Aull of CERN for performing SEY measurements, to our collaborators, to H. Padamsee for helpful discussions, and to J. Kaufman for assistance in preparing furnace runs.

REFERENCES

- [1] M. Transtrum, G. Catelani, and J. Sethna, Phys. Rev. B 83, 094505 (2011).
- [2] S. Posen and M. Liepe, in Proc. Sixteenth Conf. RF Supercond. (Paris, 2013).
- [3] S. Posen and M. Liepe, this conference, TUIOC03 (2014).
- [4] S. Aull, to be published.
- [5] A. Godeke, Supercond. Sci. Technol. 19, R68 (2006).