

DESIGN AND FABRICATION OF RACETRACK COIL ACCELERATOR MAGNETS*

K. Chow, D.R. Dietderich, S.A. Gourlay, R. Gupta, W. Harnden, A. Lietzke, A.D. McInturff, G. Millos, L. Morrison, M. Morrison, and R.M. Scanlan, Lawrence Berkeley National Laboratory, Berkeley, California

Abstract

Most accelerator magnets for applications in the field range up to 9 T utilize NbTi superconductor and a cosine theta coil design. For fields above 9 T, it is necessary to use Nb₃Sn or other strain sensitive materials, and other coil geometries that are more compatible with these materials. This paper describes our recent efforts to design a series of racetrack coil magnets that will provide experimental verification of this alternative magnet design philosophy for a dual aperture dipole magnet with the goal of reaching a field level of 15 T. The experimental program, consisting of a series of steps leading to a high field accelerator quality magnet, will be presented. The fabrication procedure for a racetrack dipole magnet utilizing Nb₃Sn superconductor and a wind and react approach will be presented.

1 INTRODUCTION

The ongoing program for the development and utilization of brittle superconductors for accelerator magnets at LBNL has been recently focused on coils with a simple racetrack geometry. High field, low cost magnets are the most likely option for significantly lowering the overall cost of a new high energy collider. In particular, we are concentrating on the development of the common coil approach [1,2] for its potential simplicity of construction and consequent cost effectiveness. The design concept, shown schematically in Figure 1, consists of a pair of racetrack coils shared between two apertures, producing fields in opposite directions.

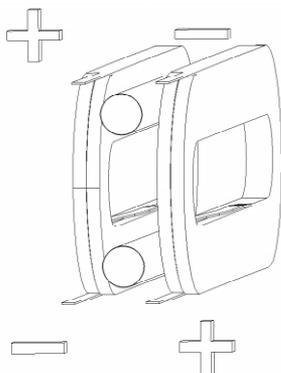


Figure 1: Common Coil Geometry

The ultimate goal of the program is to develop accelerator quality dipoles with fields up to 15 T. This will be approached by building a few lower field magnets to demonstrate the feasibility of the design, develop fabrication techniques and understand relevant performance parameters. Success will also depend on the parallel development of high quality, low cost superconductor.

2 DESIGN

2.1 Conductor and Cable

The early prototypes utilize 0.808 mm diameter strand manufactured by Teledyne Wah Chang Albany (TWCA) for the ITER project, which has a J_c of about 610 A/mm² at 12 T and 4.2 K. The first model magnet is expected to achieve a bore field of approximately 7 T. This design should produce a field of 11.3 T with a conductor J_c of 1800 A/mm², which is presently being produced. Thirty strands are wound into a Rutherford style cable with a rectangular cross section, 1.45 X 12.34 mm. The cable is insulated with a nominal 0.13 mm thick sleeve of woven S-2 glass. To reduce carbon deposits during reaction, the factory sizing is baked out and replaced with a palmitic acid sizing which leaves a minimal carbon residue.

2.2 Coil Module Design

The fundamental component of this design is the coil module, which consists of a double-layer coil contained in a support structure. The coil module components are shown in Figure 2.

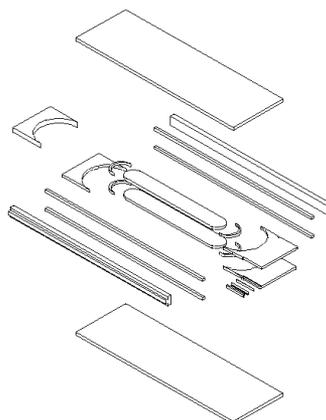


Figure 2: Coil Module Components for a Double-Layer Racetrack Coil

The preliminary design is for a 40 mm aperture magnet with emphasis on maintaining the simplicity of the racetrack geometry. The major parameters optimized were bore spacing, coil aspect ratio, high field to bore field ratio and inductance, with relatively low priority placed on field quality initially. Table 1 summarizes the coil design parameters.

Table 1: Coil Parameters

Bore Diameter	40 mm
Coil length (straight section)	50 cm
Number of turns	40
Coil configuration	double racetrack
Bore spacing	150mm
Coil Radius	40mm

2.3 Structural Support

The magnet structural support is designed for modular coil assembly, Figure 3. End forces and vertical forces (forces in the plane of the racetrack coils) are supported within the coil module. A vertical prestress of 50 MPa is applied through 50 mm thick aluminum-bronze rails running the full magnet length in the coil package and an end preload of 50 MPa is applied using a series of setscrews loaded against the end shoes. To apply horizontal prestress and structural support, the coil packages are sandwiched between stainless steel clamping bars pulled together by aluminum tension rods. The horizontal preload is 16 MPa at room temperature and increases to 30 MPa at liquid helium temperatures. When fully preloaded, the magnet coil will not separate from the island when energized. Integration of vertical and end structural support into a coil package decouples the support elements in each direction. Preload can be adjusted independently in each orthogonal direction and different coil packages can be swapped into or out of the external horizontal support framework.

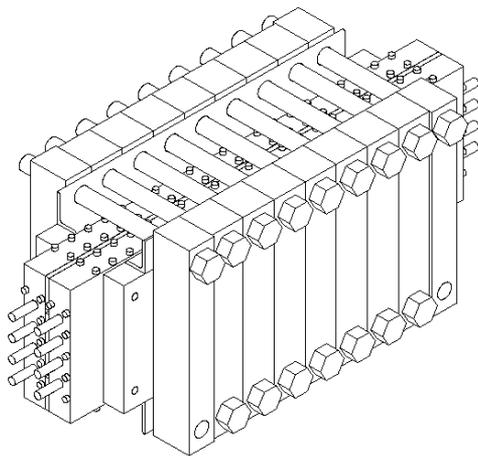


Figure 3: Coil Module Support Structure

3 FABRICATION

3.1 Coil Winding

The double-layer coils are wound around a center island (pole piece) on a flat plate with a ramp between layers to avoid internal splices. All metal parts which will be in contact with the coil are made from aluminum-bronze in order to survive the high temperature heat treatment and because of its relatively high heat transfer coefficient compared to other materials such as stainless steel. During the winding process, strips of stainless steel foil are wrapped around the cable in strategic locations to provide voltage taps. All metal parts are insulated with 0.086 mm thick strips of mica paper to augment the electrical integrity of the coil and provide a parting plane if needed. A 10 mm spacer is inserted after the 6th turn to reduce the field in the coil end.

3.2 Reaction

After winding, the coil straight section is compressed to a predetermined size by bolting spacer bars and side rails, into the upper and lower plates. The ideal coil size is determined by 10-stack measurements of insulated cable. It is important to minimize the amount of epoxy between the coil layers and thus control the mechanical properties of the composite coil. Optimal compression is achieved at a pressure between 14 and 20 MPa. End shoes are then added and the leads are carefully supported in their final positions. The pole piece is made in two parts with a gap to allow for differential thermal contraction of the conductor and components during reaction. The lead-end shoe and pole piece section are fixed in place, while the return end of the coil is allowed to move. The coil is placed in a stainless steel retort under an Argon atmosphere and reacted according to the manufacturer's recommended reaction cycle, for a two week period.

3.3 Instrumentation

Following reaction, a pair of NbTi cables are spliced to the fragile Nb₃Sn leads. The splice regions are eventually safely contained in the impregnated coil package. Four capacitance gauges are then inserted in each coil layer (One in the pole piece gap, one between the pole piece and inner turn, another between the outer turn and side rail and one between the return-end shoe and the outer turn). Finally, a 0.13 mm laminated sheet of Kapton, stainless steel and copper, containing the heater strips, readout traces and pads for the voltage taps is added to each layer, followed by a 0.13 mm sheet of glass cloth.

3.4 Epoxy Impregnation

The reacted coil is strain sensitive and must be reinforced with a glass fiber and epoxy matrix. The epoxy needs to have low viscosity in order to penetrate the glass

fiber between the coils, maintain good mechanical properties at cryogenic temperatures and have a relatively long pot life. CTD-101 [3] is a good choice for this application and has been used successfully in the past [4]. The stainless steel side rails and plates used during reaction are replaced with similar parts made of aluminum-bronze, designed to closely fit the post-reaction dimensions of the coil. Strips of mica paper are added between the outer turn of the coil and the surfaces of the side rails and end-shoes for electrical insulation. Also, the mica provides a shear plane, intended to prevent stick-slip motion under Lorentz loading. In addition, the plates, side-rails and end-shoes are mold released. The completed package is then vacuum impregnated, providing a robust module for insertion into the horizontal support structure. All surfaces in contact with the coil remain after potting, providing good surface matching and reducing the necessity for stringent part tolerances, thus another potential cost saving feature of this design.

3.5 Final Assembly

Prior to impregnation, a 0.5 mm shim is inserted between the side support rail and the top and bottom plates. The coil size, and thus the vertical preload on the coil can easily be adjusted by reducing the thickness of the shim and retightening the side bolts. The coil packages and support structure components are stacked and aligned via pins. The nuts on the aluminum tension rods are then tightened to obtain the desired preload.

4 FUTURE PROGRAM

This magnet represents the first in a series of magnets with the goal to produce a device of similar design with a field of 14 – 15 T within two years. It will be completed and tested in August. Test plans include a series of preload studies, making use of the simple support structure design. Experience gained will be used to modify the existing design to accommodate higher fields. The design also allows the magnet aperture to be easily reduced by changing the width of the internal support structure. This would create a higher field magnet. The theoretical results of such a study are shown in Figure 4 where the D20 cable is used [5].

The bore field goes up from 9.8 T for 40 mm spacing to 11.7 T for 10 mm spacing.

ACKNOWLEDGEMENTS

We wish to thank our group of talented technicians for their indispensable contributions to the design and fabrication effort in this project – Paul Bish, Roy Hannaford, Hugh Higley, Greg Hay, Nate Liggins and Jim Smithwick.

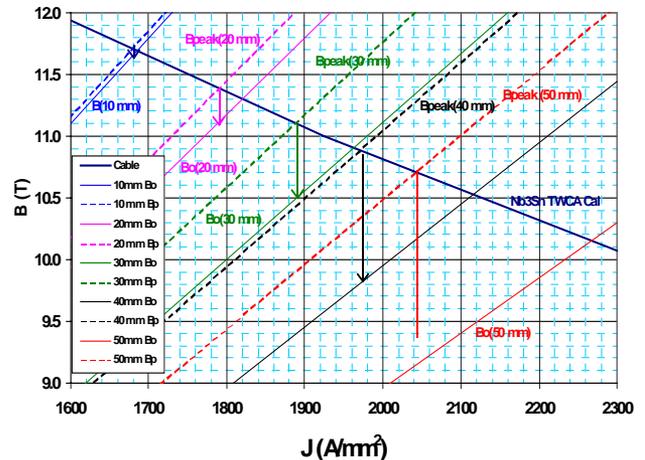


Figure 4: Expected Performance of a Double Pancake Coil with D20 Cable.

REFERENCES

- [1] G. Danby, et al., "Proceedings of the 12th International Conference on High-Energy Accelerators," Fermilab, August 11-16, 1983.
- [2] R. Gupta, "A Common Coil Design for High Field 2-IN-1 Accelerator Magnets", Particle Accelerator Conference, Vancouver, Canada, 1997.
- [3] Composites Technology Development, Inc. Boulder, CO 80303.
- [4] D. Dell'Orco, et al., "Fabrication and Component Testing Results for a Nb₃Sn Dipole Magnet", IEEE Trans. on Applied Superconductivity, vol. 5, no. 2, pp. 1000 – 1003, June, 1995.
- [5] A.D. McInturff, et al., "Test Results for a High Field (13 T) Nb₃Sn Dipole," Particle Accelerator Conference, Vancouver, Canada, May, 1997.

*This work was performed with the support of the Office of High Energy and Nuclear Physics, United States Department of Energy under contract DE-AC03-76F0098.